



INTERNATIONAL CONFERENCE
MEĐUNARODNA KONFERENCIJA

MEETING POINT OF THE SCIENCE AND PRACTICE IN THE FIELDS OF
CORROSION, MATERIALS AND ENVIRONMENTAL PROTECTION

*STECIŠTE NAUKE I PRAKSE U OBLASTIMA KOROZIJE,
ZAŠTITE MATERIJALA I ŽIVOTNE SREDINE*

PROCEEDINGS

KNJIGA RADOVA

Under the auspices of the
MINISTRY OF EDUCATION, SCIENCE AND TECHNOLOGICAL
DEVELOPMENT OF THE REPUBLIC OF SERBIA

Pod pokroviteljstvom
MINISTARSTVO PROSVETE, NAUKE I TEHNOLOŠKOG RAZVOJA
REPUBLIKE SRBIJE

September 13-16, 2021 : : Tara Mountain, Serbia

CIP - Katalogizacija u publikaciji
Narodna biblioteka Srbije, Beograd

620.193/.197(082)(0.034.2)

621.793/.795(082)(0.034.2)

667.6(082)(0.034.2)

502/504(082)(0.034.2)

66.017/.018(082)(0.034.2)

INTERNATIONAL Conference YUCORR (22 ; 2021 ; Tara)

Meeting point of the science and practice in the fields of corrosion, materials and environmental protection [Elektronski izvor] : proceedings = Stecište nauke i prakse u oblastima korozije, zaštite materijala i životne sredine : knjiga radova / XXII YuCorr International Conference = XXI YuCorr [Jugoslovenska korozija] Međunarodna konferencija, September 13-16, 2021, Tara Mountain, Serbia = [organized by] Serbian Society of Corrosion and Materials Protection ... [et al.] ; [organizatori Udruženje inženjera Srbije za koroziju i zaštitu materijala ... [et al.] ; [editors, urednici Miomir Pavlović, Miroslav Pavlović, Marijana Pantović Pavlović]. - Beograd : Serbian Society of Corrosion and Materials Protection UJSKOZAM : Udruženje inženjera Srbije za koroziju i zaštitu materijala UJSKOZAM, 2021 (Beograd : Serbian Society of Corrosion and Materials Protection UJSKOZAM : Udruženje inženjera Srbije za koroziju i zaštitu materijala UJSKOZAM). - 1 elektronski optički disk (CD-ROM) ; 12 cm

Sistemska zahteva: Nisu navedeni. - Nasl. sa naslovne strane dokumenta. - Tekst na engl. i srp. jeziku.

- Tiraž 200. - Bibliografija uz većinu radova. - Abstracts.

ISBN 978-86-82343-28-8

a) Премази, антикорозиони -- Зборници б) Превлаке, антикорозионе -- Зборници в)

Антикорозиона заштита -- Зборници г) Животна средина -- Заштита -- Зборници д) Наука о материјалима -- Зборници

COBISS.SR-ID 48091145

XXII YUCORR – International Conference | Međunarodna konferencija

PUBLISHED AND CD BURNED BY | IZDAVAČ I NAREZIVANJE CD

SERBIAN SOCIETY OF CORROSION AND MATERIALS PROTECTION (UISKOZAM)

UDRUŽENJE INŽENJERA SRBIJE ZA KORZIJU I ZAŠTITU MATERIJALA (UISKOZAM),

Kneza Miloša 7a/II, 11000 Beograd, Srbija, tel/fax: +381 11 3230 028, office@sitzam.org.rs; www.sitzam.org.rs

FOR PUBLISHER | ZA IZDAVAČA Prof. dr MIOMIR PAVLOVIĆ, predsednik UISKOZAM

SCIENTIFIC COMMITTEE | NAUČNI ODBOR: Prof. dr M. G. Pavlović, Serbia – President

Prof. dr Đ. Vaštag, Serbia; Dr M. M. Pavlović, Serbia; Prof. dr D. Vuksanović, Montenegro;

Prof. dr D. Čamovska, North Macedonia; Prof. dr M. Antonijević, Serbia; Prof. dr S. Stopić, Germany;

Prof. dr R. Zejnilović, Montenegro; Prof. dr L. Vrsalović, Croatia; Dr N. Nikolić, Serbia;

Dr I. Krastev, Bulgaria; Prof. dr B. Grgur, Serbia; Prof. dr M. Gvozdrenović, Serbia;

Prof. dr S. Hadži Jordanov, North Macedonia; Prof. dr R. Fuchs Godec, Slovenia;

Prof. dr J. Stevanović, Serbia; Dr V. Panić, Serbia; Dr M. Mihailović, Serbia;

Prof. dr V. Marić, Bosnia and Herzegovina; Prof. dr J. Jovičević, Serbia; Prof. dr D. Jevtić, Serbia;

Dr F. Kokalj, Slovenia; Prof. dr A. Kowal, Poland; Prof. dr Prof. dr M. Gligorić, Bosnia and Herzegovina;

Prof. dr M. Tomić, Bosnia and Herzegovina; Prof. Dr B. Arsenović, Bosnia and Herzegovina

ORGANIZING COMMITTEE | ORGANIZACIONI ODBOR: Dr Miroslav Pavlović – president

Dr Nebojša Nikolić – vice president; Dr Marija Mihailović – vice president

Prof. dr Miomir Pavlović; Aleksandar Putnik B.Sc.; Dr Vladimir Panić; Jelena Slepčević, B.Sc.;

Dr Vesna Cvetković; Prof. dr Milica Gvozdrenović; Zagorka Bešić, B.Sc.; Gordana Miljević, B.Sc.;

Miomirka Anđić, B.Sc.; Dr Marija Matić; Marijana Pantović Pavlović, M.Sc.; Dr Dragana Pavlović;

Dr Sanja Stevanović; Lela Mladenović – secretary

EDITORS | UREDNICI: Prof. dr Miomir Pavlović, Dr Miroslav Pavlović, Marijana Pantović Pavlović, M.Sc.

SCIENTIFIC AREA | OBLAST: CORROSION AND MATERIALS PROTECTION | KORROZIJA I ZAŠTITA MATERIJALA

PAGE LAYOUT | KOMPJUTERSKA OBRADA I SLOG: Dr Miroslav Pavlović

CIRCULATION | TIRAŽ: 200 copies | primeraka

PUBLICATION YEAR | GODINA IZDANJA: 2021

ISBN 978-86-82343-28-8



Ovaj PDF fajl sadrži elektronsku Knjigu radova prezentovanih u okviru Međunarodne konferencije **XXII YuCorr**. U knjizi su **plavom bojom** obeleženi aktivni linkovi ka pojedinim njenim delovima, iz Sadržaja do naznačenih stranica.

This PDF file contains Proceedings presented on the **XXII YuCorr** International Conference. It can be easily navigated through the book contents by a single click on the appropriate links in Contents (**showed in blue**).

Autori snose punu odgovornost za sadržaj, originalnost, jezik i gramatičku korektnost sopstvenih radova.

Authors bear full responsibility for the content, originality, language and grammatical correctness of their own works.

**XXII YUCORR IS ORGANIZED BY
ORGANIZATORI XXII YUCORR-a**



SERBIAN SOCIETY OF CORROSION AND MATERIALS PROTECTION

Udruženje Inženjera Srbije za Koroziju i Zaštitu Materijala



**INSTITUTE OF CHEMISTRY, TECHNOLOGY AND METALLURGY,
UNIVERSITY OF BELGRADE**

*Institut za Hemiju, Tehnologiju i Metalurgiju,
Univerzitet u Beogradu*



UNION OF ENGINEERS AND TECHNICIANS OF SERBIA, BELGRADE

Savez Inženjera i Tehničara Srbije



ENGINEERING ACADEMY OF SERBIA

Inženjerska Akademija Srbije

**XXII YUCORR IS ORGANIZED UNDER THE AUSPICES OF THE
MINISTRY OF EDUCATION, SCIENCE AND TECHNOLOGICAL
DEVELOPMENT OF THE REPUBLIC OF SERBIA**



***XXII YUCORR JE FINANSIJSKI POMOGLO
MINISTARSTVO PROSVETE, NAUKE I TEHNOLOŠKOG RAZVOJA
REPUBLIKE SRBIJE***

SPONSORS | SPONZORI

INTERNATIONAL SOCIETY OF ELECTROCHEMISTRY, Switzerland

SAVEZ INŽENJERA I TEHNIČARA SRBIJE, Beograd

HELIOS SRBIJA a.d., Gornji Milanovac

METAL CINKARA d.o.o., Inđija

SURTEC ČAČAK d.o.o., Čačak

ALFATERM d.o.o., Čačak

INSTITUT ZA PREVENTIVU d.o.o., Novi Sad

EKP ELKER a.d., Prijedor, Republika Srpska, B&H

EKO ZAŠTITA d.o.o., Bijeljina, Republika Srpska, B&H

IPIN d.o.o., Bijeljina Republika Srpska, B&H

HEMIPRODUKT d.o.o., Novi Sad

INSTITUT ZA OPŠTU I FIZIČKU HEMIJU, Beograd

SZR "GALVA", Kragujevac

NOVOHEM d.o.o., Šabac

Electrodeposition of Nd and Pr onto W from fluoride based melts *Elektrohemijsko taloženje Nd i Pr na W iz fluoridnih rastopa*

Vesna S. Cvetković^{1,*}, Dominic Feldhaus², Nataša M. Vukićević¹, Nebojša D. Nikolić¹, Bernd Friedrich², Jovan N. Jovićević¹

¹*Department of Electrochemistry, Institute of Chemistry, Technology and Metallurgy, University of Belgrade, Njegoševa 12, 110000 Belgrade, Serbia*

²*IME Process Metallurgy and Metal Recycling, Institute of RWTH Aachen University, Intzestrass 3, 52056 Aachen, Germany*

**v.cvetkovic@ihm.bg.ac.rs*

Abstract

Electrodeposition of neodymium and praseodymium metal from molten $NdF_3+PrF_3+LiF+0.5wt.\%Pr_6O_{11}+0.5wt.\%Nd_2O_3$ electrolytes on W was investigated using voltammetry at 1050 °C. The square wave voltammetry confirmed that Nd electrodeposition is a two-step reduction process: first, involving one electron exchange ($Nd(III)\rightarrow Nd(II)$) and second, involving two electrons exchange ($Nd(II)\rightarrow Nd(0)$). However, praseodymium deposition proceeds as an one-step process involving exchange of three electrons ($Pr(III)\rightarrow Pr(0)$). Nd and Pr metals were electrodeposited applying potentiostatic mode. The working electrode surface was analyzed by X-ray diffraction after Nd and Pr co-deposition.

Keywords: *neodymium; praseodymium; fluoride melts; SWV; XRD*

Izvod

Elektrohemijsko taloženje neodijuma i prazeodijuma iz fluoridnog $NdF_3+PrF_3+LiF+0.5wt.\%Pr_6O_{11}+0.5wt.\%Nd_2O_3$ rastopa na W radnoj elektrodi ispitivano je pomoću voltametrijskih tehnika na 1050 °C. Voltametrija sa pravougaonim talasima (SWV, square wave voltammetry) potvrdila je da je elektrohemijsko taloženje Nd proces koji se odvija u dva koraka: prvi, uključuje razmenu od jednog elektrona ($Nd(III)\rightarrow Nd(II)$) i drugi korak, uključuje razmenu dva elektrona ($Nd(II)\rightarrow Nd(0)$). Međutim, taloženje prazeodijuma uključuje izmenu tri elektrona ($Pr(III)\rightarrow Pr(0)$) u jednom koraku. Nd i Pr su elektrohemijski taloženi primenom potenciostatskog režima. Nakon elektrohemijskog taloženja Nd i Pr površina radne elektrode analizirana je rengensko-difrakcionom tehnikom.

Ključne reči: *neodijum; prazeodijum; fluoridni rastopi; SWV; XRD*

Introduction

As the demand for Nd-Pr alloys had increased over time, the design and creation of the new processes for providing sufficient amount of these rare earth elements are required [1–3]. Neodymium–iron–boron permanent magnets ($Nd_2Fe_{14}B$, or NdFeB), depending on the application, contains about 31–32 wt.% of rare earth elements (REEs), mainly neodymium and praseodymium (Nd+Pr) [4]. Due to the complexity associated with the continuous growth of rare earth solid wastes, a simple, and environmentally friendly recycling process will play an important role for future sustainable primary supply of REEs. There are several approaches to the recovery of rare earth elements from the end-of-life (EOL) magnets: hydrometallurgical and pyrometallurgical processes, liquid metal extraction, molten salt electrolysis [5,6]. Among these processes, molten salt electrolysis offers an attractive solution in lights of its high purity of end product, low energy consumption, and high efficiency [5]. For electrolytic production of neodymium and praseodymium

via molten salt electrolysis, in terms of efficiency and environmental footprint, molten fluorides or chlorides are commonly used as electrolytes [5].

In the present investigation concerning the electroreduction processes of neodymium(III) and praseodymium(III) ions in fluoride molten salts system we demonstrate that metallic neodymium and praseodymium can be electrodeposited on a chosen inert electrode. More specifically, the reaction mechanism of neodymium and praseodymium deposition was studied in the fluoride based molten salts containing the rare earth oxides, in order to ensure appropriate potential for increase of Nd and Pr metal deposited on the tungsten cathode surface.

Experimental

Neodymium fluoride (NdF_3 , $\geq 99.9\%$), praseodymium fluoride (PrF_3 , $\geq 99.9\%$), lithium fluoride (LiF , $\geq 99.5\%$), neodymium oxide (Nd_2O_3 , $\geq 99.9\%$) and praseodymium oxide (Pr_6O_{11} , $\geq 99.9\%$) were purchased from Treibacher, Althofen, Austria. The electrolyte composition was: 45.5wt.% NdF_3 +45.5wt.% PrF_3 +9wt.% LiF +0.5wt.% Pr_6O_{11} +0.5wt.% Nd_2O_3 . The graphite crucible, filled with the salt mixture, was placed into the steel electrochemical cell, the lid was closed and the cell was placed into a resistance furnace. A three electrode configuration was employed, in which as a working electrode was used a tungsten 2 mm diameter rod (EWG 99.95%), reference electrode was made from tungsten (1 mm diameter rod) and the counter electrode was glassy carbon rod ($>99.99\%$ HTW SIGRADUR® G). The details of the electrochemical cell set up and procedure of electrolyte preparation have already been reported elsewhere [7,8]. The measurements started after the molten salt was stable at the experimental temperature of 1050 °C. The electrochemical measurements: cyclic voltammetry (CV), square wave voltammetry (SWV) and open-circuit chronopotentiometry, were controlled by an IviumStat potentiostat (5 A/10V; Ivium Technologies). The deposition was carried out in a potentiostic mode, which was monitored as current density versus time. The structure analysis of the deposit was revealed by X-ray diffraction (XRD), Philips PW 1050 powder diffractometer.

Results and Discussion

It was cyclic voltammetry to be employed first in the study of electrochemical reactions related to Nd(III) and Pr(III) ions redox transitions on W working electrode in molten NdF_3 + PrF_3 + LiF +0.5wt.% Pr_6O_{11} +0.5wt.% Nd_2O_3 salts. Fig. 1 shows typical CV obtained on a W working electrode when cathodic end potential, E_C , was gradually swept from the initial potential, E_I , towards more negative values.

Within the applied potential range, the voltammograms exhibited three current waves C_1 , C_2 and C_3 in the cathodic sections and corresponding anodic counterparts A_1 , A_2 and A_3 in the anodic sections of the scanned potential range.

In the cathodic run peak C_1 starting at ≈ -0.400 V vs. W and its anodic counterpart A_1 at ≈ -0.360 V vs. W should be attributed to the redox transition $\text{Nd(III)} \leftrightarrow \text{Nd(II)}$. At potentials negative compared to -0.400 V vs. W a second reduction peak C_2 at ≈ -0.520 V vs. W was observed. This peak we associate with electrodeposition of Nd, ($\text{Nd(II)} + 2e^- \rightarrow \text{Nd(0)}$). During the anodic scan direction the electrochemical dissolution of Nd is manifested at potential around -0.500 V vs. W, as an anodic peak A_2 . Third cathodic peak C_3 starting from about -0.720 V vs. W can be assigned to electrochemical reduction of Pr(III) to Pr(0), and the anodic peak A_3 at -0.620 V vs. W is associated with the dissolution of previously deposited Pr metal, in other words $\text{Pr(0)} \rightarrow \text{Pr(III)}$.

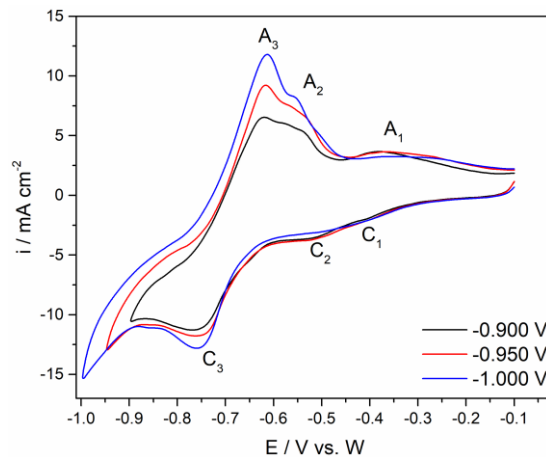


Figure 1. CV recorded on W working electrode, $E_i = -0.100$ V vs. W to different cathodic end potential E_C , obtained with sweep rate of 100 mVs^{-1} in $\text{NdF}_3 + \text{PrF}_3 + \text{LiF} + 0.5 \text{ wt. \% Pr}_6\text{O}_{11} + 0.5 \text{ wt. \% Nd}_2\text{O}_3$ electrolyte, $T = 1050$ °C.

To further investigate the electrochemical co-deposition of neodymium and praseodymium from $\text{NdF}_3 + \text{PrF}_3 + \text{LiF} + 0.5 \text{ wt. \% Pr}_6\text{O}_{11} + 0.5 \text{ wt. \% Nd}_2\text{O}_3$ electrolyte, a set of square wave voltammograms (SWV) at different frequencies was obtained on W electrode. The results are shown in Fig. 2. The potentials of all three reduction current peaks recorded by SWV at: $C_1 \approx -0.450$ V vs. W, $C_2 \approx -0.650$ V vs. W, and $C_3 \approx -0.720$ V vs. W correspond very well to C_1 , C_2 and C_3 recorded in the voltammograms presented in Fig. 1 obtained within the same potential range under the same conditions. In the case of a reversible reaction, the electron transfer number can be expressed by Eq. (1) which is a mathematical analysis based on the half-peak width recorded by SWV:

$$W_{1/2} = 3.52RT/nF \quad (1)$$

where $W_{1/2}$ is the half-peak width (V), T is the temperature (K), R represents the universal gas constant ($\text{J mol}^{-1} \text{ K}^{-1}$), n is the number of exchanged electrons, and F is the Faraday constant (96485 C mol^{-1}).

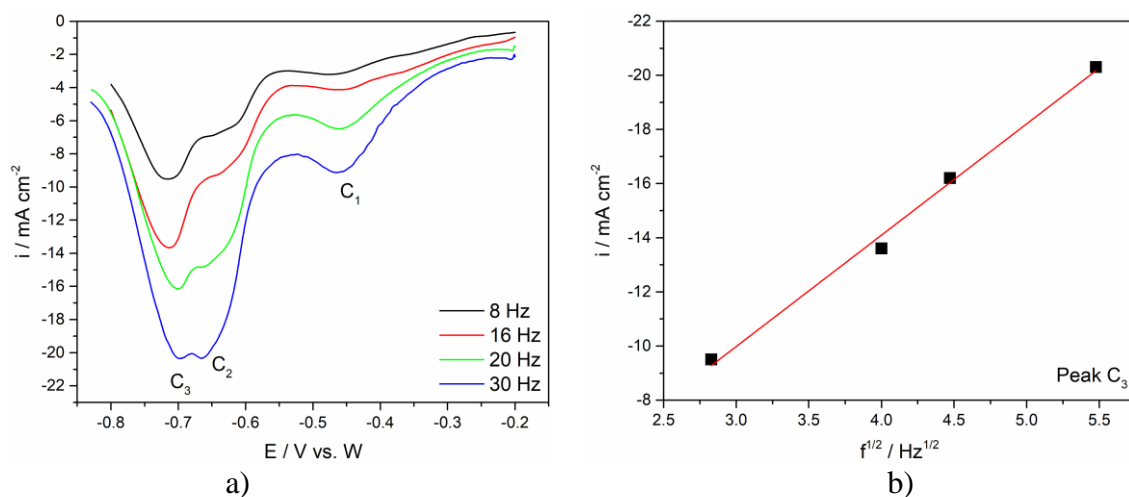


Figure 2. (a) SWV obtained with different frequencies on W WE; pulse height: 25 mV; potential step: 1 mV; electrolyte $\text{NdF}_3 + \text{PrF}_3 + \text{LiF} + 0.5 \text{ wt. \% Pr}_6\text{O}_{11} + 0.5 \text{ wt. \% Nd}_2\text{O}_3$; (b) Variation of the peak current density vs. the square root of the frequency in the Fig. 2a) for peak C_3 .

The plot of the peak C_3 current density on SWV from Fig. 2a) vs. the square root of frequency is presented in Fig. 2b). It was found to be a linear relationship. Since the criterion of linearity for the peak C_3 was established Gaussian fitting model was applied and the exchange electron number was calculated using Eq. (1) [6,9]. It was found that the exchanged electron number for peak C_3 is 2.87, close to 3. Accordingly it was concluded that the reduction of praseodymium(III): namely $\text{Pr(III)} \rightarrow \text{Pr(0)}$, on W in this electrolyte is only one electrochemical three electron exchange step. This conclusion confirmed that the electrode reactions reflected by the current waves C_2/A_2 and C_1/A_1 can be assigned to the redox transition of Nd(III) ions to Nd metal in two steps: $\text{Nd(III)} \leftrightarrow \text{Nd(II)}$ and $\text{Nd(II)} \leftrightarrow \text{Nd(0)}$. This is in accordance with previous literature reports [7–9].

In order to establish Nd and Pr co-deposition a potentiostatic deposition at the potential negative to the C_3 peak potentials recorded in Fig. 1 and 2a) was performed, and W working electrode surface was analyzed afterwards by the XRD, Fig. 3.

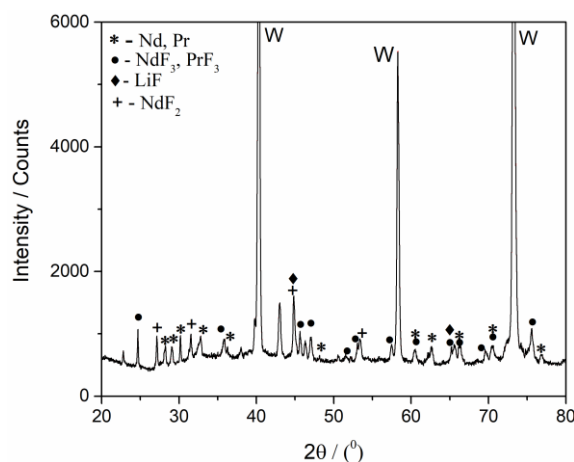


Figure 3. XRD pattern of the W working electrode after deposition at -0.900 V vs. W for 240 min, from molten $\text{NdF}_3 + \text{PrF}_3 + \text{LiF} + 0.5\text{wt.}\% \text{Pr}_6\text{O}_{11} + 0.5\text{wt.}\% \text{Nd}_2\text{O}_3$ electrolyte, at 1050 °C, (the solidified electrolyte was removed from the electrode).

The diffraction peaks at around 2θ values: 28.1° , 29.1° , 30.2° , 32.8° , 36.3° , 48.1° , 60.5° , 62.6° , 67.0° , 70.4° , 76.8° , 77.3° , have to be attributed to both metals, Nd and Pr [JCPDS No. 03-065-3424 and JCPDS No. 01-089-2921]. Actually, both metals exhibit similar chemical properties, hexagonal crystal lattice and very similar lattice parameters. The presence of melt residue, NdF_3 , PrF_3 , LiF in the diffractogram could not be avoided. However, NdF_2 was also detected and it seems that it was formed through disproportionation reaction between Nd metal electrodeposited and Nd(III) ions in the electrolyte: $\text{Nd(0)} + 2\text{Nd(III)} \rightarrow 3\text{Nd(II)}$. This is in accordance with previous literature reports by some other authors describing neodymium electrodeposition from neodymium oxyfluoride melts, at temperatures close to or above 1323 K [7–9].

Conclusion

In order to investigate electrochemical co-deposition of Nd and Pr, the electrochemical behaviour of Nd(III) and Pr(III) ions in molten $\text{NdF}_3 + \text{PrF}_3 + \text{LiF} + 0.5\text{wt.}\% \text{Pr}_6\text{O}_{11} + 0.5\text{wt.}\% \text{Nd}_2\text{O}_3$ were first studied on W electrode. Cyclic voltammetry and square wave voltammetry indicated that the reduction of Nd(III) ions to the metal proceeds as a two-step reduction process: $\text{Nd(III)} \rightarrow \text{Nd(II)}$ and $\text{Nd(II)} \rightarrow \text{Nd(0)}$, whilst the reduction of Pr(III) ions to the metal is a one-step reduction process: $\text{Pr(III)} \rightarrow \text{Pr(0)}$. Neodymium and praseodymium were successfully electrodeposited on W cathode by applying constant potential, from fluoride based Nd, Pr and Li molten salts containing rare earth oxides (Nd_2O_3 and Pr_6O_{11}). The findings of this study could be a promising final link towards intended integral recycling process for used NdFeB magnet scraps.

Acknowledgements

V.S.C. and N.M.V. acknowledge the financial support for the investigation received from the Ministry of Education, Science and Technological Development of the Republic of Serbia (Grant No.451-03-9/2021-14/200026). Part of the research was supported by the funds of the bilateral research project (ID: 451-03-01344/2020-09/8) supported by the Ministry of Education, Science and Technological Development of the Republic of Serbia and German Academic Exchange Service (DAAD).

References

1. K. Yasuda, K. Kondo, T. Nohira, R. Hagiwara, Electrochemical Formation of Pr–Ni Alloys in LiF–CaF₂–PrF₃ and NaCl–KCl–PrCl₃ Melts, *J. Electrochem. Soc.*, **161**, D3097–D3104, 2014.
2. S. Stopic, B. Friedrich, Advances in Understanding of the Application of Unit Operations in Metallurgy of Rare Earth Elements, *Metals (Basel)*, **11**, 978, 2021.
3. P. Sarfo, A. Das, C. Young, Extraction and optimization of neodymium from molten fluoride electrolysis, *Sep. Purif. Technol.*, **256**, 117770, 2021.
4. Y. Yang, A. Walton, R. Sheridan, K. Güth, R. Gauß, O. Gutfleisch, M. Buchert, B. M. Steenari, T. Van Gerven, P. T. Jones, K. Binnemans, REE Recovery from End-of-Life NdFeB Permanent Magnet Scrap: A Critical Review, *J. Sustain. Metall.*, **3**, 122–149, 2017.
5. S. Senanu, A. P. Ratvik, H. Gudbrandsen, A. M. Martinez, A. Støre, W. Gebarowski, Dissolution and Online Monitoring of Nd and Pr Oxides in NdF₃–PrF₃–LiF Electrolytes, *Metals (Basel)*, **11**, 326, 2021.
6. Y. Yang, C. Lan, L. Guo, Z. An, Z. Zhao, B. Li, Recovery of rare-earth element from rare-earth permanent magnet waste by electro-refining in molten fluorides, *Sep. Purif. Technol.*, **233**, 116030, 2020.
7. V. S. Cvetković, D. Feldhaus, N. M. Vukićević, T. S. Barudžija, B. Friedrich, J. N. Jovićević, Investigation on the electrochemical behaviour and deposition mechanism of neodymium in NdF₃–LiF–Nd₂O₃ melt on Mo electrode, *Metals (Basel)*, **10**, 576, 2020.
8. V. S. Cvetković, N. M. Vukićević, D. Feldhaus, T. S. Barudžija, J. S. Stevanović, B. Friedrich, J. N. Jovićević, Study of Nd Deposition onto W and Mo Cathodes from Molten Oxide-Fluoride Electrolyte, *Int. J. Electrochem. Sci.*, **15**, 7039–7052, 2020.
9. C. Huang, X. Liu, Y. Gao, S. Liu, B. Li, Cathodic processes of neodymium(III) in LiF–NdF₃–Nd₂O₃ melts, *Faraday Discuss.*, **190**, 339–349, 2016.